

REPORT NUMBER:

HKGT05089383



Number: HKGT05089383

TEST REPORT

Applicant: BOOSTER(DONGGUAN)PLASTIC PRODUCTS CO LTD
NO. 497 NORTH OF TANGXIA RD
TANGXIA TOWN DONGGUAN CITY
GUANGDONG PROVINCE
CHINA


Date: Jan 20, 2022

Sample Description As Declared :

No. Of Sample : 1 roll
Sample Description : Elastic Staple pin / Plastic Staple
Colour : Clear
Brand : BOOSTER
Country of Origin : Dongguan
Product End Uses : packing material
Fibre Content : TPU
Date Received/Date Test Started : Nov 11, 2021

For any queries on this report, you are welcome to contact our customer service representatives:
Carita Lam - Mobile phone and Whatsapp (852) 91713077 or email to carita.lam@intertek.com
Steve Yu - Mobile phone and Whatsapp (852) 63290534 or email to steve.yu@intertek.com

For and on behalf of
Intertek Testing Services Hong Kong Limited



Teddy Y. N. Chung
Director



Page 1 Of 8



TEST REPORT

Tests Conducted (As Requested By The Applicant)

- 1 Standard Test Method For Determining Anaerobic Biodegradation Of Plastic Materials Under High-Solids Anaerobic-Digestion Conditions (ASTM D5511-18):

PROJECT DESCRIPTION:

Elastic Staple Pin in clear were submitted for testing under standard ASTM D5511. This test method covers the determination of the degree and rate of anaerobic biodegradation of plastic materials in high-solids anaerobic conditions. The test materials are exposed to a methanogenic inoculum derived from anaerobic digesters operating only on pretreated household waste. The anaerobic decomposition takes place under high-solids (more than 30 % total solids) and static non-mixed conditions. This test method is designed to yield a percentage of conversion of carbon in the sample to carbon in the gaseous form under conditions found in high-solids anaerobic digesters, treating municipal solid waste.

INOCULUM COLLECTION AND CONDITIONING

The anaerobic digested sewage sludge (Figure 1) mixed with household waste. To make the sludge adapted and stabilized during a short post-fermentation at 53°C, the sludge was pre-incubated (one week) at 53°C. This means that the concentrated inoculum was not fed but allowed to post ferment the remains of previously added organics allowing large easily biodegradable particles were degraded during this period and reduce the background level of biogas from the inoculums itself.



Figure 1: Anaerobic microbial inoculum

INOCULUM PROPERTIES

A sample of the anaerobic digested sewage sludge was analyzed for pH, percent dry solids, and volatile solids, as well as, the amount of CO₂ and CH₄ evolution during the testing. Table 1 lists the results of this initial testing.

TEST REPORT

Tests Conducted (As Requested By The Applicant)

METHODOLOGY:

Inoculum Medium: Remove enough inoculum (approximately 15 kg) from the post-fermentation vessel and mix carefully and consistently by hand in order to obtain a homogeneous medium. Test three replicates each of a blank (inoculum only), Positive control (Reference material) (thin-layer chromatography cellulose), negative control (polyethylene)(Optional), and the test substance being evaluated.

Manually mix 1000 g wet weight (at least 20 % dry solids) of inoculum in a small container for a period of 2 to 3 min with 15 to 100 g of volatile solids of the test substance or the controls for each replicate. For the three blanks containing inoculum only, manually mix 1000 g of the same inoculum in a small container for a period of 2 to 3 min with the same intensity as was done for the other vessels containing test substance or controls. Determine the weight of the inoculum and test substance added to each individual Erlenmeyer flask accurately. Add the mixtures to a 2-L wide-mouth Erlenmeyer flask and gently spread and compact the material evenly in the flask to a uniform density.

After placing the Erlenmeyer flask in incubator, connect it with the gas collection device. Incubate the Erlenmeyer flasks in the dark or in diffused light at 52°C for thermophilic conditions, the incubation time shall be run until no net gas production is noted for at least five days from both the Positive control (Reference material) and test substance reactors. Control the pH of the water used to measure biogas production to less than two by adding HCl.

ANAEROBIC DIGESTER SETUP FOR THE PLASTIC BIODEGRADATION

The biodegradation testing of sample was performed in the digester as shown in the (Figure-2).

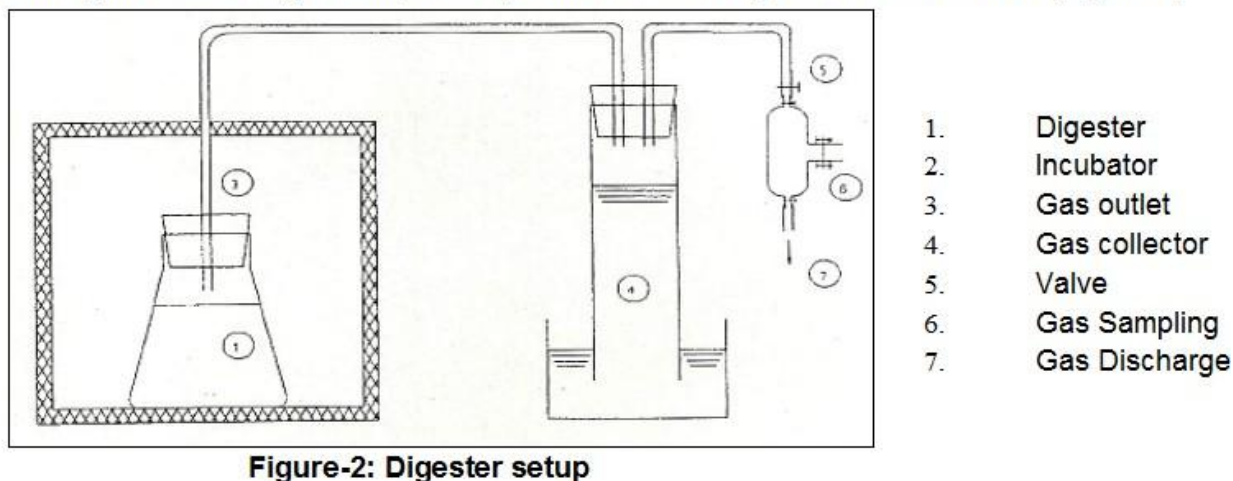


Figure-2: Digester setup

RESULT:

The most important biochemical characteristics of the inoculum such as pH, Volatile Solids, NH_4^+-N and dry solids were studied.

TEST REPORT

Tests Conducted (As Requested By The Applicant)

Table 1: Results of Initial testing of the anaerobic digested sewage sludge

Parameters	Requirement	Actual results
pH	7.5 to 8.5	7.92
Kjeldahl nitrogen	0.5 to 2 g/kg wet weight	1.30
Dry Solids at 105 °C	>20%	40.0
Volatile Solids at 550 °C	Below 1 g/kg wet weight	0.8

The biogas volume in the gas sampling bag was measured (Table-2). Presence of gas in the gas collector of Positive control (Reference material) indicated that the inoculum was viable and gas displacement was observed both in Positive control (Reference material) and Test Sample.

ASTM D5511 states that for the test to be considered valid, the Positive control (Reference material) must achieve 70 % within 45 days with deviation less than 20% of the mean between the replicates.

Positive control (Reference material) showed 70.85% on 27th day with less than 20% of the mean difference between the replicates.

The gas displacement observed after 45 days is as shown in the table below.

Table-2: Biogas volume of the evolved gas during the biodegradation process at 45 days

Biodegradation Test	Total Volume 45 days (mL)
Inoculum	1135
Positive control (Reference material)	10900
Test Sample	4630

TEST REPORT

Tests Conducted (As Requested By The Applicant)

Colonization of bacteria at some places were observed under the microscope (Fig-3). This shows the process of biodegradation has begun.

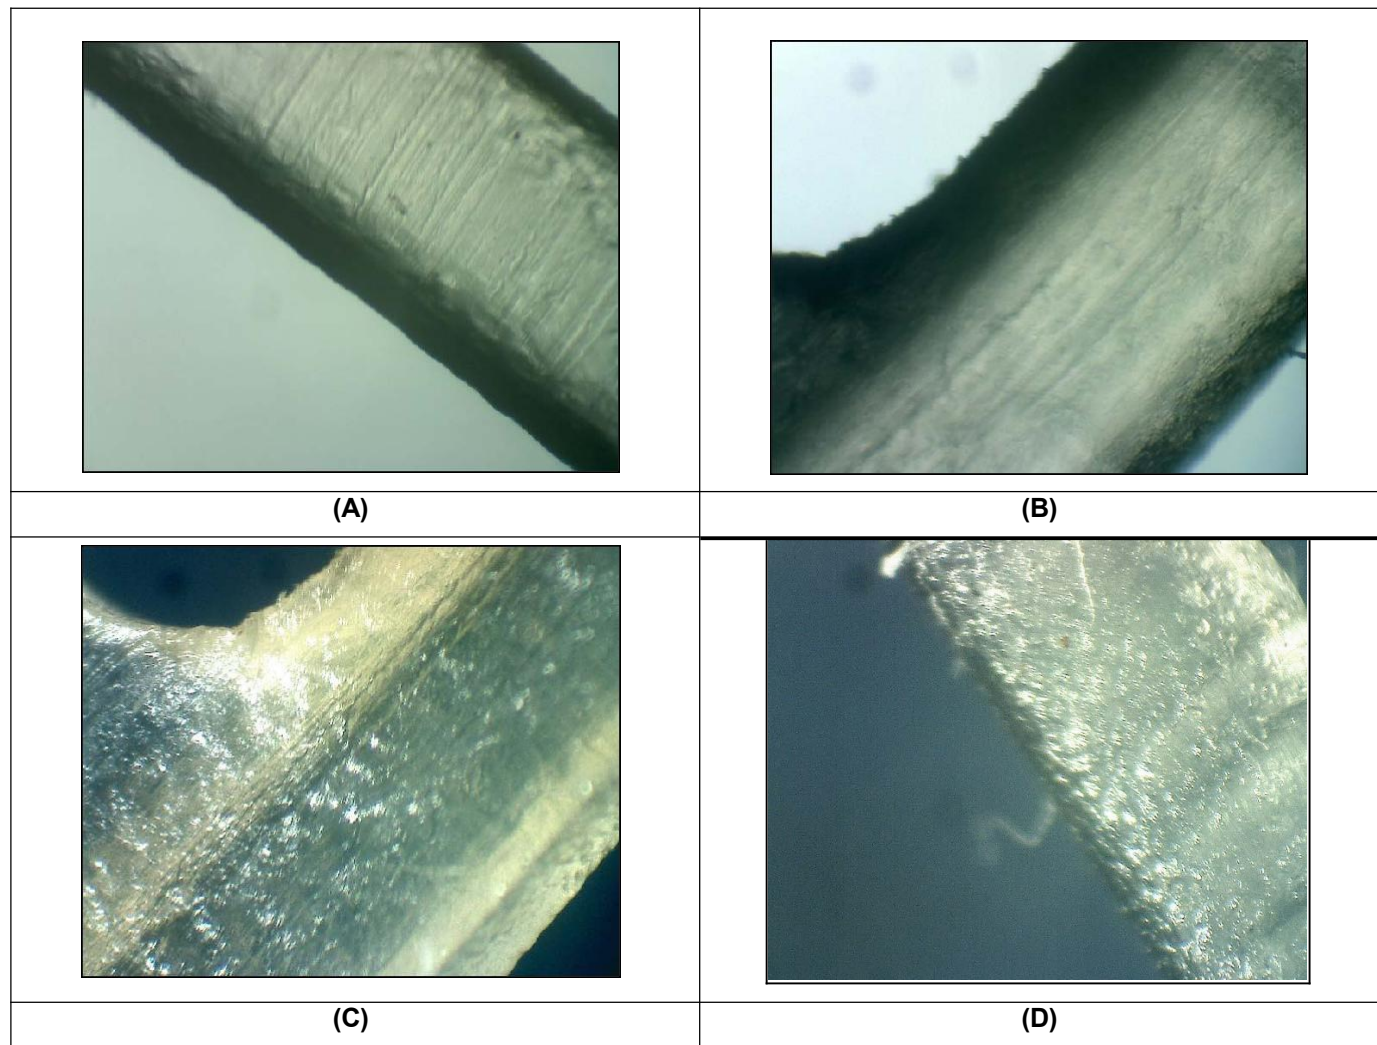


Figure 3: Microscopic image of Test samples Before and After 45 days Incubation Condition
A & B – Unexposed Test Sample to anaerobic biodegradation process
C & D – Exposed Test Sample to anaerobic biodegradation process

The percent biodegradation of Positive control (Reference material) and Test sample was calculated by the measured cumulative carbon dioxide and methane production from each flask after subtracting carbon dioxide evolution and methane evolution from the blank samples at the end of 45 days of testing. Calculations were based on Total Organic Carbon obtained of both Positive control (Reference material) and Test sample.

TEST REPORT

Tests Conducted (As Requested By The Applicant)

Table-3: Percentage biodegradability of Test sample with respect to Positive control (Reference material) Cellulose.

Group	Inoculum control	Positive control (Reference material)	Test sample
Weight	1000 ml	10.0851	10.6359
Total volume (ml)	1135.00	10900.00	4630.00
% CH ₄	8.38	37.50	24.02
Volume of CH ₄ (ml)	95.11	4087.50	1112.13
weight of CH ₄ (g)	0.06	2.68	0.73
% CO ₂	7.43	33.50	31.47
Volume of CO ₂ (ml)	84.33	3651.50	1457.06
Weight of CO ₂ (g)	0.17	7.23	2.88
Total weight of carbon in grams	0.09	3.96	1.33
Theoretical weight of carbon in grams (Ci)	-	4.24	7.059
Biodegradation	-	0.91	0.175
% Biodegradation	-	91.27	17.56

The Percent weight loss was calculated based on the initial weight and final weight of the sample after the 45 days study.


TEST REPORT

Tests Conducted (As Requested By The Applicant)

Table 4: Percent weight loss of Test sample.

Average Initial Weight (grams)	10.6359
Average Final Weight (grams)	10.3598
Percent Weight Loss (%)	2.59

Biodegradation of the samples determined based on conversion of carbon from the test material to carbon in the gaseous phase (CH₄ and CO₂) can be observed in graph 1.

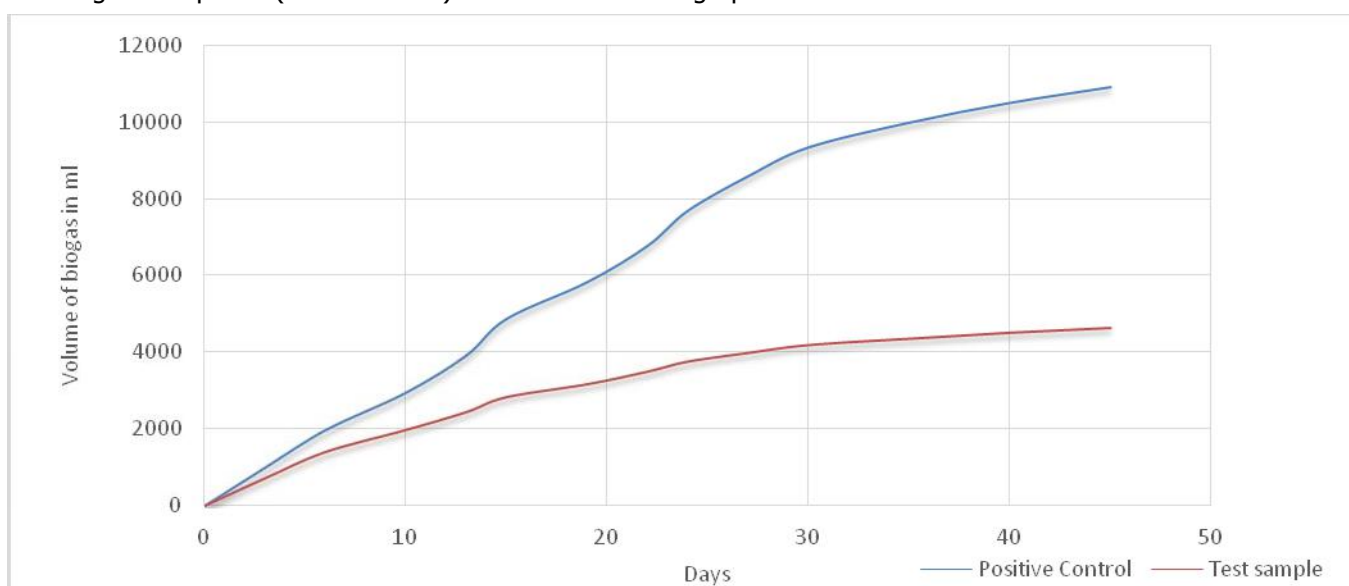

Graph-1: The percent biodegradation of the Test Sample determined based on conversion of carbon from the Test material to carbon in the gaseous phase (CH₄ and CO₂)

TEST REPORT

Tests Conducted (As Requested By The Applicant)

CONCLUSION:

Considering the cumulative gas production as observed in Table 2 & 3 and its analysis indicates that the process of biodegradation has occurred. After 45 days of incubation, the level of biodegradation for the Positive control (Reference material) was 91.27% while the Test sample showed **17.56 %** relative to the Positive control (Reference material).

Remark: The test was subcontracted to laboratory under Intertek group.

End of Report

Except where explicitly agreed in writing, all work and services performed by Intertek is subject to our standard Terms and Conditions which can be obtained at our website: <http://www.intertek.com/terms/>. Intertek's responsibility and liability are limited to the terms and conditions of the agreement.

This report is made solely on the basis of your instructions and / or information and materials supplied by you and provide no warranty on the tested sample(s) be truly representative of the sample source. The report is not intended to be a recommendation for any particular course of action, you are responsible for acting as you see fit on the basis of the report results. Intertek is under no obligation to refer to or report upon any facts or circumstances which are outside the specific instructions received and accepts no responsibility to any parties whatsoever, following the issue of the report, for any matters arising outside the agreed scope of the works. This report does not discharge or release you from your legal obligations and duties to any other person. You are the only one authorized to permit copying or distribution of this report (and then only in its entirety). Any such third parties to whom this report may be circulated rely on the content of the report solely at their own risk.

This report shall not be reproduced, except in full.