


T(oC)	K3	Diss
29	3263	0.013
39	3285	0.013
45	3298	0.013
55	3362	0.013
60	3426	0.014
64	3506	0.014
69	3596	0.014
74	3680	0.014
79	3770	0.014
88	3900	0.014
93	4001	0.014
100	4104	0.014
105	4204	0.014
110	4305	0.014
115	4406	0.014
120	4508	0.014
125	4580	0.014
130	4650	0.014
135	4743	0.014
140	4770	0.014
145	4866	0.014
150	4944	0.014
155	5066	0.014
160	5126	0.014
165	5256	0.014
170	5380	0.014
175	5488	0.013
180	5607	0.013
185	5799	0.013
190	5910	0.013
195	6033	0.013
200	6198	0.014
205	6429	0.014
210	6579	0.014

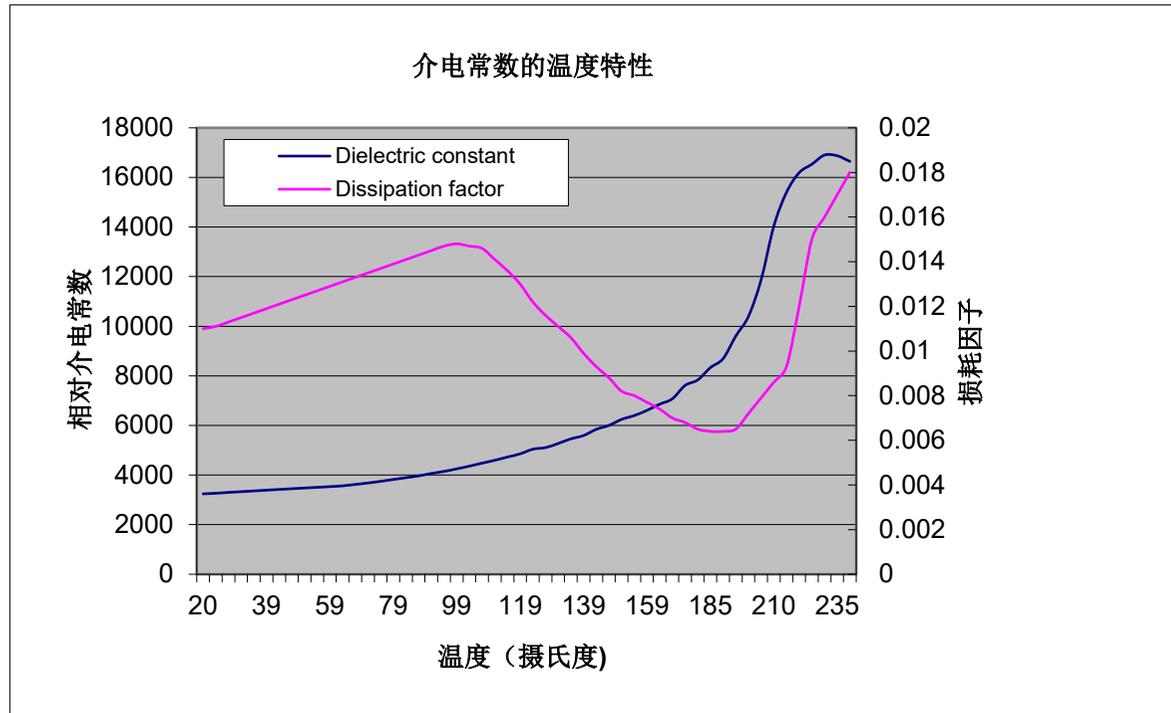

Block was fired on 8-8-02

215	6943	0.014
220	7155	0.014
225	7352	0.014
230	7685	0.011
235	7979	0.01
240	8339	0.01
245	8869	0.01
250	9307	0.01
255	9913	0.01
260	10956	0.01
265	11885	0.011
270	13182	0.012
275	14273	0.012
280	14838	0.012
285	15489	0.011
290	15825	0.01
295	16022	0.009
300	16094	0.009
305	16002	0.009

Curie point at around 260oC.

Tested on 4-11-2003

T(oC)	K3	Diss
20	3242	0.011
23	3267	0.0111
27	3300	0.0113
31	3331	0.0115
35	3360	0.0117
39	3391	0.0119
43	3420	0.0121
47	3449	0.0123
51	3478	0.0125
55	3506	0.0127
59	3534	0.0129
63	3565	0.0131
67	3622	0.0133

71	3681	0.0135
75	3747	0.0137
79	3823	0.0139
83	3895	0.0141
87	3966	0.0143
91	4065	0.0145
95	4147	0.0147
99	4250	0.0148
103	4360	0.0147
107	4480	0.0146
111	4596	0.0141
115	4727	0.0136
119	4855	0.013
123	5042	0.0122
127	5107	0.0116
131	5272	0.0111
135	5460	0.0106
139	5593	0.0099
143	5843	0.0093
147	6002	0.0088
151	6244	0.0082
155	6400	0.008
159	6607	0.0077
165	6857	0.0074
170	7074	0.007
175	7612	0.0068
180	7834	0.0065
185	8331	0.0064
190	8692	0.0064
195	9601	0.0065
200	10396	0.0072
205	11873	0.0079
210	14032	0.0086
215	15395	0.0093
220	16190	0.012
225	16531	0.015

230	16901	0.016
235	16872	0.017
240	16645	0.018